



Journal of Advanced Research in Fluid Mechanics and Thermal Sciences

Journal homepage:

https://semarakilmu.com.my/journals/index.php/fluid_mechanics_thermal_sciences/index

ISSN: 2289-7879



Thermal and Mechanical Properties of Thermoplastic Cassava Starch/Beeswax Reinforced with Cogon Grass Fiber

Ridhwan Jumaidin^{1,*}, Harith Hilman Abdul Halim¹, Alia Ruzanna Aziz², Meysam Keshavarz³, Tuan Suhaimi Salleh⁴, Rushdan Ahmad Ilyas^{5,6}, Fudhail Abdul Munir⁷, Mastura Mohamad Taha¹, Nadlene Razali⁷, Abdul Rafeq Saleman⁷, Ahmad Fuad Ab Ghani¹, Nuzaimah Mustafa¹, Nazri Huzaimi Zakaria¹, Mohd Adrinata Shaharuzzaman⁷, Syahibudil Ikhwan Abdul Kudus¹, Mohd Yuhazri Yaakob¹

- ¹ Fakulti Teknologi Kejuruteraan Mekanikal dan Pembuatan, Universiti Teknikal Malaysia Melaka, Hang Tuah Jaya, 76100 Durian Tunggal, Melaka, Malaysia
- ² Technology Innovation Institute (TII), Advanced Materials Research Centre, PO Box 9639, Masdar City, Abu Dhabi, United Arab Emirates
- ³ The Hamlyn Centre, Institute of Global Health Innovation, Imperial College London, Bessemer Building, South Kensington Campus, Exhibition Road, London, SW7 2AZ, United Kingdom
- ⁴ Bahagian Inovasi, Penyelidikan dan Pembangunan Kejuruteraan, Pusat Kecemerlangan Kejuruteraan dan Teknologi JKR (CREaTE), Jalan Kemus Simpang Ampat, 78000 Alor Gajah, Melaka, Malaysia
- ⁵ School of Chemical and Energy Engineering, Faculty of Engineering, Universiti Teknologi Malaysia (UTM), Johor Bahru 81310, Malaysia
- ⁶ Centre for Advanced Composite Materials (CACM), Universiti Teknologi Malaysia (UTM), Johor Bahru 81310, Malaysia
- ⁷ Fakulti Kejuruteraan Mekanikal, Universiti Teknikal Malaysia Melaka, Hang Tuah Jaya, 76100 Durian Tunggal, Melaka, Malaysia

ARTICLE INFO

Article history:

Received 29 January 2022

Received in revised form 1 May 2022

Accepted 9 May 2022

Available online 8 June 2022

Keywords:

Thermoplastic starch; cogon grass; water absorption

ABSTRACT

The aim of this paper is to investigate the effect of cogon grass fiber (CGF) on the thermal and mechanical properties of thermoplastic cassava starch (TPCS)/beeswax matrix. The alteration of TPCS/beeswax reinforced with cogon grass fiber was performed by incorporating various amount of CGF (0,10,20,30,40 wt.%) into the polymer matrix. The samples were then evaluated using thermogravimetric analysis and tensile test. The findings showed that the thermal properties of the composite were slightly improved as the CGF content increase. The mechanical test showed that the tensile strength and tensile modulus increased with the addition of the CGF. However, the elongation at break showed a decreased pattern following the increasing content of CGF compared to the 0% of fiber content. In general, the findings from this study have shown that the TPCS/beeswax reinforced with the CGF composite has improved the functional properties of the composites compared to the TPCS matrix.

1. Introduction

In recent, the concern about protection of ecological systems is rapidly growing. Non-biodegradable and environmental pollution are the side effects of petroleum based synthetic polymers. These polymers affect wildlife severely, due to its poor disposition [1]. Together with increasing environmental regulations, the depletion of petroleum resources acts synergistically to

* Corresponding author.

E-mail address: ridhwan@utem.edu.my

<https://doi.org/10.37934/arfmts.96.1.5359>

provide the impetus for new materials and products that are environmentally compatible and independent fossil fuel [2]. However, the increased demand for environmentally friendly plastics, such as bio-based plastics produced from renewable resources, and biodegradable plastics that are degrading in the environment to build a more sustainable society and managing global waste and environmental problems [3].

Among bio-based plastic, starch is one of the most promising due to the abundant, low cost, renewable, and totally biodegradable in nature [4,5]. Starch can be converted into thermoplastic material with the presence of heat and shear; hence, it can be processed by using conventional plastic processing technique such as extruder and injection molding [6,7]. However, pure thermoplastic starch has limitation such as poor mechanical properties which limits the potential application of this bioplastic in the industry.

In recent, natural-based reinforcement has gain increasing interest due to the high demand for more sustainable and environmentally friendly manufacturing approach [8-10]. The performance of this material is quite promising as reported in the previous studies [11-13]. On the other hand, cogon grass or *Imperata Cylindrica* grass are part of the Poacea (Graminae) grass family. This plant also known as jap grass, blady grass, spear grass, and Lalang in Malaysia. This grass is well known because of its troublesome traits which is the rough edges of the mature cogon grass leaves and silica bodies all over the leaves cause the grass is not edible for the animals. Instead, this grass can bring injuries to the animals. This grass also can grow aggressively throughout the tropical and subtropical areas across the world [14]. Nevertheless, cogon grass composed of several elements which are cellulose, hemicelluloses, lignin, pectins and extractives which serve as potential reinforcement source for composite material. In our previous study, cogon grass has shown good reinforcement effect which makes this material as potential reinforcement for polymer composites [15].

Beeswax is natural wax derive from bees which is widely used in food and cosmetic industry. Apart from that, beeswax portrays good properties such as ability to block moisture migration and improve product's shelf life and remain its main application as a product coating [6]. In our previous study, incorporation of beeswax has successfully improved the thermoplastic starch rigidity and reduce its moisture sensitivity [6].

Hence, even though there are previous study reported on using cogon grass fiber as reinforcement, however, none has been found on using this fiber as reinforcement for thermoplastic starch/beeswax composites. Hence, this study investigates the behavior of thermoplastic cassava starch modified by incorporation of beeswax and cogon grass fiber. The thermal and mechanical properties of the composites will be evaluated in this study.

2. Materials and Methodology

2.1 Materials

Food grade cassava starch was procured from Antik Sempurna Sdn Bhd, Malaysia. Glycerol used as a plasticizer was purchased from QReC Chemical. Beeswax was purchased from Sigma Aldrich chemical. Cogon grass was obtained from Ayer Keroh, Melaka, Malaysia. The extraction process of Cogon grass fiber was carried out using water retting method. Minimum time required for the water retting is 2 weeks depends on the Cogon grass texture itself. When the leaves of Cogon grass become soft enough, the leaves need to be tear to smaller parts to ease the following grinding process. After tearing the leaves to smaller parts, the leaves need to be dried under the sunshine for few hours. The dried leaves of Cogon grass need to be cut more into smaller pieces before underwent the grinding process that will produce fine Cogon grass fiber.

2.2 Sample Fabrication

The modification of TPCS/Beeswax reinforced with Cogon grass fiber was performed by mixing different amount of Cogon grass fiber (0, 10, 20, 30, 40 wt.%) into the polymer matrix using high speed mixer (Table 1). The mixture was pressed at 145 °C for 1 hour into 3 mm thickness plate using GoTech hot press machine. The prepared samples were stored in close desiccator until further testing.

Table 1

Amount of cogon grass fiber as reinforcement

Composites	TPCS/Beeswax (%)	Fiber loading (%)
0	100	0
10%	90	10
20%	80	20
30%	70	30
40%	60	40

2.3 Thermal Testing: Thermo-gravimetric Analysis (TGA)

Thermogravimetric analysis was carried out to identify the thermal degradation behaviour of the material with respect to weight loss due to temperature increment. TGA was conducted with a Mettler-Toledo AG, Analytical from Schwerzenbach, Switzerland. The specimen weighs around 10±2 mg. The analysis was performed in an aluminium pan under a dynamic nitrogen atmosphere in the temperature range 25 to 900°C at heating rate of 10°C min⁻¹.

2.4 Mechanical Testing: Tensile

The specimens for tensile tests were prepared according to the ASTM D638. The test was carried using a Universal Testing Machine (INSTRON 5969) with a 5 kN load cell; the crosshead speed is maintained at 5 mm/min. The testing needs to be set at room temperature of 23 ± 1 °C and relative humidity of 50 ± 5%.

3. Result and Discussion

3.1 Thermo-gravimetric Analysis

The decomposition and thermal stability of TPCS/beeswax reinforced with CGF were presented in thermogravimetric analysis (TGA) and derivative thermogravimetric (DTG) curves in Figure 1 and Figure 2. Figure 1 shows the TGA curves obtained from the TPCS/Beeswax reinforced with the CGF composite. The first phase of degradation in temperature range of 0°C to 200°C was attributed to the evaporation of water and glycerol. After that, the change of the weight loss for TPCS/Beeswax reinforced with CGF composite in temperature range between 150°C to 180°C was mainly attributed to decomposition of three major chemical components of the natural fibers; hemicellulose, cellulose and lignin) [16]. Besides that, another study by Sarifuddin *et al.*, [17], stated that decomposition process that take place at temperature in range up to 300°C where the thermal degradation of starch carbon chains occurred.

After completion of hemicellulose decomposition, the cellulose decomposes approximately at temperature of 320°C and followed up by the hardest component to 68 decompose which is the lignin that started as early of 160°C and degrade slowly up to 900°C for complete decomposition [16].

Degradation above 500°C may possibly related to the decomposition of carbonate fiber leading to the formation of char. In the final decomposition stage of the composites, the remaining char were oxidated [18]. can be observed that the composite with the highest fiber content which is 40% have higher thermal stability compared to the 0% of fiber content. The justification is mainly due to the fiber loading in the composite.

Meanwhile, Figure 2 shows the DTG curves obtained from the TPCS/Beeswax reinforced with the CGF composites. It is clearly visible that the first peak of the composites (maximum decomposition) after integration with CGF was slightly deviated into the lower temperature which is compliance with the result shown in TGA curve, implying enhanced the thermal stability. The weight loss at the maximum decomposition phase was decreased following the increase of CGF content. According to Lomelí-Ramírez *et al.*, [19], addition of the fiber with the starch matrix enhances the thermal stability when the fiber and the matrix adhere properly, reducing mass loss in the sample.

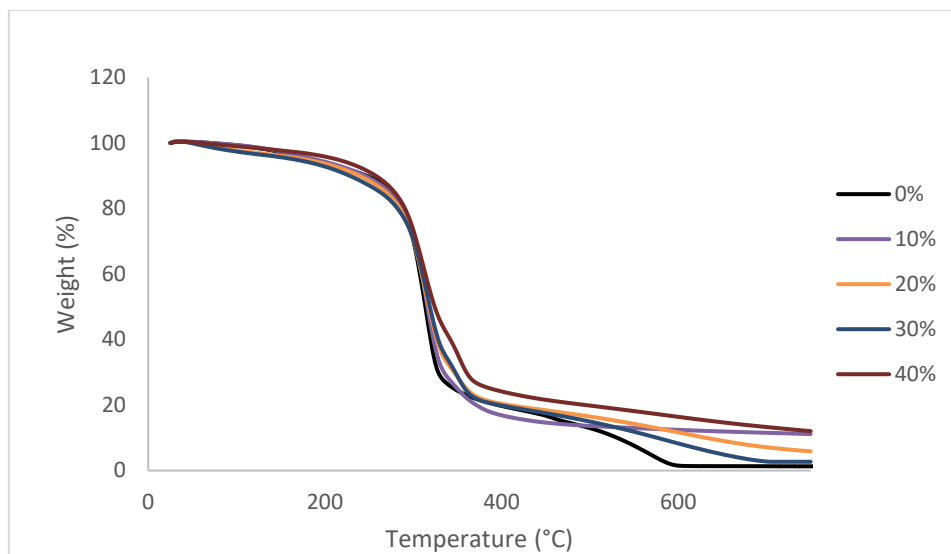


Fig. 1. TGA curve of TPCS/Beeswax + CGF composite

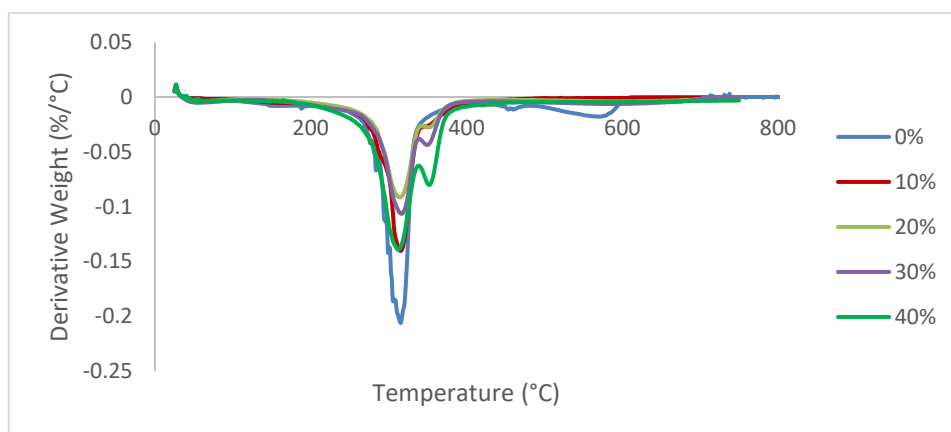


Fig. 2. DTG curve of TPCS/Beeswax reinforced with CGF composite

3.2 Tensile Properties

The alteration of the composition of thermoplastic cassava starch has affected the mechanical characteristics of the thermoplastic cassava starch. The effect of CGF addition on the TPCS/Beeswax composites were shown in the Figure 4 until Figure 6, which is the tensile strength, tensile modulus

and elongation at break. Based on Figure 4, the tensile strength of TPCS/Beeswax reinforced with CGF showed a significant increment with an increase fiber content from 0% until 30%. This can be associated with the reinforcing effect of the CGF initiated by the interactions between the TPCS matrix and the cogon grass reinforcement and by the good surface wetting morphology as observed from SEM micrographs in Figure 11. However, there was a slight reduction at 40% of CGF. The reduction of strength at this point might be attributed to larger/higher content of fiber [20].

Meanwhile for the tensile modulus showed a major improvement until 40% even though the tensile strength was slightly decreased. According to Sarifuddin *et al.*, [17], it was anticipated that the fiber additions would improve the modulus due to inclusion in the soft matrix of rigid filler particles. Therefore, this finding suggests that the fiber inside the composites existed to have the stiffening effect.

Besides that, the elongation of the composites was already high initially before addition of Cogon grass fiber. Refer to the Figure 6, the elongation begun to decline when 10% of cogon grass fiber is added into the TPCS/Beeswax matrix. The declination continues until 40% of cogon grass fiber content. The lower concentration of starch that leads to the decrease in elongation in breaks can be related to these phenomena. Therefore, lower content of fiber have improved elongation values, whereas higher content of fiber has provided a decreasing elongation.

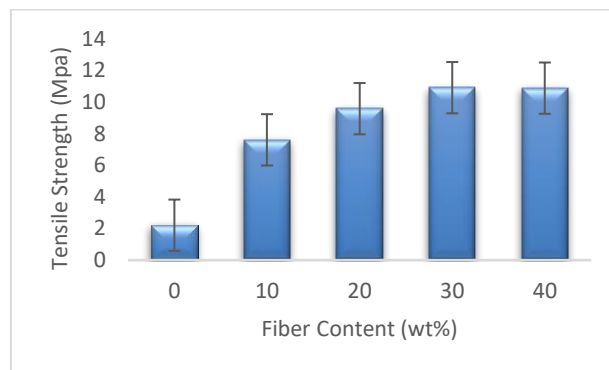


Fig. 4. Tensile strength of TPCS/Beeswax reinforced with CGF

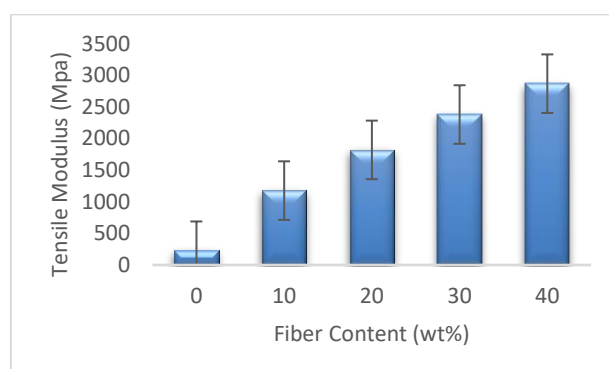


Fig. 5. Tensile modulus of TPCS/Beeswax reinforced with CGF

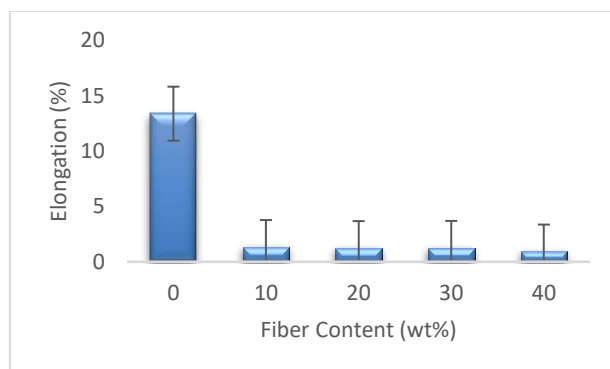


Fig. 6. Elongation at break of TPCS/Beeswax reinforced with CGF

4. Conclusion

The biopolymer composite derived from cassava starch and incorporation of cogon grass fiber were successfully prepared via high speed mixing and hot pressing in this study. The thermal properties of TPCS/beeswax reinforced with CGF composite were successfully evaluated. TGA test indicates that the incorporation of CGF significantly improved the thermal stability of the composite. The mechanical properties of TPCS/beeswax reinforced with CGF composite were successfully evaluated. The incorporation of CGF essentially enhanced the tensile strength and tensile modulus but decrease the elongation at break of the composite. Overall, this finding shows that addition of cogon grass fiber has improve the functional properties of this material.

Acknowledgement

The authors would like to express sincere gratitude to Universiti Teknikal Malaysia Melaka and Ministry of Higher Education Malaysia for the financial support provided through research grant RACER/2019/ FTKMP-CARE/F00413, the conference proceeding was supported by publication incentive grant JURNAL/FTK/2018/Q00004.

References

- [1] Keskin, Gülsah, Gülnur Kızıl, Mikhael Bechelany, Céline Pochat-Bohatier, and Mualla Öner. "Potential of polyhydroxyalkanoate (PHA) polymers family as substitutes of petroleum based polymers for packaging applications and solutions brought by their composites to form barrier materials." *Pure and Applied Chemistry* 89, no. 12 (2017): 1841-1848. <https://doi.org/10.1515/pac-2017-0401>
- [2] Mohanty, Amar K., Manjusri Misra, and Lawrence T. Drzal, eds. *Natural fibers, biopolymers, and biocomposites*. CRC Press, 2005. <https://doi.org/10.1201/9780203508206.ch1>
- [3] Iwata, Tadahisa. "Biodegradable and bio-based polymers: future prospects of eco-friendly plastics." *Angewandte Chemie International Edition* 54, no. 11 (2015): 3210-3215. <https://doi.org/10.1002/anie.201410770>
- [4] Hafila, K. Z., R. Jumaidin, R. A. Ilyas, M. Z. Selamat, and Fahmi Asyadi Md Yusof. "Effect of palm wax on the mechanical, thermal, and moisture absorption properties of thermoplastic cassava starch composites." *International Journal of Biological Macromolecules* 194 (2022): 851-860. <https://doi.org/10.1016/j.ijbiomac.2021.11.139>
- [5] Diyana, Z. N., R. Jumaidin, Mohd Zulkefli Selamat, Ihwan Ghazali, Norliza Julmohammad, Nurul Huda, and R. A. Ilyas. "Physical properties of thermoplastic starch derived from natural resources and its blends: a review." *Polymers* 13, no. 9 (2021): 1396. <https://doi.org/10.3390/polym13091396>
- [6] Diyana, Z. N., R. Jumaidin, M. Z. Selamat, and M. S. M. Suan. "Thermoplastic starch/beeswax blend: Characterization on thermal mechanical and moisture absorption properties." *International Journal of Biological Macromolecules* 190 (2021): 224-232. <https://doi.org/10.1016/j.ijbiomac.2021.08.201>
- [7] Kamaruddin, Zatil Hafila, Ridhwan Jumaidin, Rushdan Ahmad Ilyas, Mohd Zulkefli Selamat, Roziela Hanim Alamjuri, and Fahmi Asyadi Md Yusof. "Biocomposite of Cassava Starch-Cymbopogan Citratus Fibre: Mechanical, Thermal

- and Biodegradation Properties." *Polymers* 14, no. 3 (2022): 514. <https://doi.org/10.3390/polym14030514>
- [8] Bakhori, Siti Nadia Mohd, Siti Nur Fatin Zuikafly, Fauzan Ahmad, and Mohamad Zaki Hassan. "Tensile properties for MWCNT filled jute-Epoxy composites." *Journal of Advanced Research in Applied Mechanics* 31, no. 1 (2017): 16-21.
- [9] Yew, Ming Kun, Ming Chian Yew, Lip Huat Saw, Siang Kang Lim, Jing Han Beh, Foo Wei Lee, and Leong Tatt Loh. "Influence of High Performance Hybrid Polyvinyl Alcohol-Polypropylene Fibres on Mechanical Properties of Oil Palm Shell Lightweight Concrete." *Journal of Advanced Research in Applied Mechanics* 49, no. 1 (2018): 1-11.
- [10] Aziz, Annis Nazirah Abdul, and Roszilah Hamid. "Mechanical properties and impact resistance of hybrid kenaf and coir fibre reinforced concrete." *Journal of Advanced Research in Applied Mechanics* 47, no. 1 (2018): 1-10.
- [11] Farahana, R. N., A. G. Supri, and P. I. Teh. "Tensile and water absorption properties of eggshell powder filled recycled high-density polyethylene/ethylene vinyl acetate composites: effect of 3-aminopropyltriethoxysilane." *Journal of Advanced Research in Materials Science* 5, no. 1 (2015): 1-9.
- [12] Loh, X. H., Mohd Ahadlin Mohd Daud, and M. Zulkefli Selamat. "A Study on Fibre Length and Composition of Kenaf-Polypropylene (K-PP) Composite for Automobile Interior Parts." *Journal of Advanced Research in Materials Science* 1, no. 1 (2014): 22-27.
- [13] Yee, Koh Chai, Azwan Iskandar Azmi, Wan Azani Mustafa, Aiman Akmal Abdul Nasir, and Tan Chye Lih. "Effect of Notch and Notch Size on the Flexural Performance of Flax Fibre Composites." *Journal of Advanced Research in Applied Mechanics* 52, no. 1 (2018): 1-7.
- [14] Mohd Kassim, Angzazs Sari, Ashuvila Mohd Aripin, Nadiah Ishak, and Muhd Hafeez Bin Zainulabidin. "Cogon grass as an alternative fibre for pulp and paper-based industry: on chemical and surface morphological properties." In *Applied Mechanics and Materials*, vol. 773, pp. 1242-1245. Trans Tech Publications Ltd, 2015. <https://doi.org/10.4028/www.scientific.net/AMM.773-774.1242>
- [15] Jumaidin, Ridhwan, Muhammad Afif Akmal Khiruddin, Zulhelmi Asyul Sutan Saidi, Mohd Sapuan Salit, and Rushdan Ahmad Ilyas. "Effect of cogon grass fibre on the thermal, mechanical and biodegradation properties of thermoplastic cassava starch biocomposite." *International Journal of Biological Macromolecules* 146 (2020): 746-755. <https://doi.org/10.1016/j.ijbiomac.2019.11.011>
- [16] Sahari, J., S. M. Sapuan, E. S. Zainudin, and M. A. Maleque. "Thermo-mechanical behaviors of thermoplastic starch derived from sugar palm tree (*Arenga pinnata*)." *Carbohydrate Polymers* 92, no. 2 (2013): 1711-1716. <https://doi.org/10.1016/j.carbpol.2012.11.031>
- [17] Sarifuddin, Norshahida, Hanafi Ismail, and Zuraida Ahmad. "The Effect of Kenaf Core Fibre Loading on Properties of Low Density Polyethylene/Thermoplastic Sago Starch/Kenaf Core Fiber Composites." *Journal of Physical Science* 24, no. 2 (2013): 97-115. <https://doi.org/10.15376/biores.8.3.4238-4257>
- [18] Jumaidin, Ridhwan, Salit M. Sapuan, Mohammad Jawaid, Mohamad R. Ishak, and Japar Sahari. "Thermal, mechanical, and physical properties of seaweed/sugar palm fibre reinforced thermoplastic sugar palm Starch/Agar hybrid composites." *International Journal of Biological Macromolecules* 97 (2017): 606-615. <https://doi.org/10.1016/j.ijbiomac.2017.01.079>
- [19] Lomelí-Ramírez, María Guadalupe, Satyanarayana G. Kestur, Ricardo Manríquez-González, Setsuo Iwakiri, Graciela Bolzon De Muniz, and Thais Sydenstricker Flores-Sahagun. "Bio-composites of cassava starch-green coconut fiber: Part II-Structure and properties." *Carbohydrate Polymers* 102 (2014): 576-583. <https://doi.org/10.1016/j.carbpol.2013.11.020>
- [20] Edhirej, Ahmed, S. M. Sapuan, Mohammad Jawaid, and Nur Ismarrubie Zahari. "Cassava/sugar palm fiber reinforced cassava starch hybrid composites: Physical, thermal and structural properties." *International Journal of Biological Macromolecules* 101 (2017): 75-83. <https://doi.org/10.1016/j.ijbiomac.2017.03.045>